

Phase diagrams of noncentrosymmetric superconductors

Hiroshi Shimahara

*Department of Quantum Matter Science, ADSM,
Hiroshima University, Higashi-Hiroshima 739-8530, Japan*

(Dated: September 28, 2012)

Noncentrosymmetric superconductors with various types of pairing interactions are systematically examined with particular focus on phenomena that originate from the differences of the Fermi surfaces split by strong spin-orbit coupling. In particular, when the spin-orbit coupling increases and one of the split Fermi surfaces disappears, the phase diagram and the structure of the gap function change drastically. For example, we examine the conditions for transition from full-gap states to line-node states (FLT), which may explain differences in experimental results between noncentrosymmetric superconductors $\text{Li}_2\text{Pd}_3\text{B}$ and $\text{Li}_2\text{Pt}_3\text{B}$ discovered recently. The dominant pairing interactions and the gap functions can be predicted to some extent by comparing the theoretical and experimental results in these compounds. For example, if the FLT occurs by replacing Pd with Pt, it is most likely that the superconductivity is mainly induced by charge-charge interactions, and if this is the case, the superconductivities in $\text{Li}_2\text{Pd}_3\text{B}$ and $\text{Li}_2\text{Pt}_3\text{B}$ are an s-wave nearly-spin-triplet state and a d-wave state that has both spin-singlet and triplet components of comparable weights, respectively. Comparing the theoretical phase diagrams in a simple model, it is found that the FLT occurs in a wider and realistic parameter region for the charge-charge interactions, *i.e.*, where short-range Coulomb repulsion is strong and p-wave and d-wave interactions are attractive, while it occurs in narrower and rather unrealistic parameter regions for the interactions of magnetic origin. It is also found that d-wave spin-triplet pairing may occur, when the pairing interactions are of magnetic origin and anisotropic in the spin space.

PACS numbers: 74.20.-z, 74.25.Dw

I. INTRODUCTION

Recently, superconductors without inversion symmetry have been studied extensively due to their unconventional features [1–17]. The strong spin-orbit coupling results in splitting of the electronic bands, in which the direction of the electron spin depends on the momentum. As a result, the Cooper pairs are not purely of spin-singlet or of spin-triplet. Furthermore, inter-band pairing is forbidden, when the spin-orbit coupling is so strong that the energy difference of the spin-orbit split bands is larger than the magnitude of the gap function.

Among those noncentrosymmetric superconductors, we are interested in the ternary borides $\text{Li}_2\text{Pd}_3\text{B}$ and $\text{Li}_2\text{Pt}_3\text{B}$ [11, 12], because their superconductivity exhibits completely different behaviors in spite of the same crystal structures. In the nuclear magnetic resonance (NMR) measurements in $\text{Li}_2\text{Pd}_3\text{B}$, Nishiyama *et al.* observed that the nuclear spin relaxation rate T_1^{-1} exhibited the coherence peak just below T_c , and the spin susceptibility decreased below T_c [13]. These results indicate that the gap function is isotropic, and has components of antiparallel spin pairing. On the other hand, in $\text{Li}_2\text{Pt}_3\text{B}$, the relaxation rate T_1^{-1} did not exhibit any coherence peak, and was proportional to T^3 below T_c [14]. These behaviors indicate that the gap function has line nodes. The low-temperature penetration depth $\lambda(T)$ measured by Yuan *et al.* exhibited the BCS-like behavior in $\text{Li}_2\text{Pd}_3\text{B}$, while it exhibited a linear temperature dependence in $\text{Li}_2\text{Pt}_3\text{B}$, which also supports existence of the line nodes [15].

In $\text{Li}_2\text{Pt}_3\text{B}$, the Knight shift remained unchanged

across T_c [14] in contrast to that in $\text{Li}_2\text{Pd}_3\text{B}$. The theoretical explanation for this behavior seems difficult as follows. If the behavior indicates that the spin susceptibility remains unchanged across T_c , antiparallel-spin pairing is excluded. On the other hand, as Frigeri *et al.* have showed [3], the d-vector $\mathbf{d}$ must be parallel to the direction of the momentum dependent spin axis $\hat{\mathbf{g}}(\mathbf{k})$ in noncentrosymmetric superconductors with strong spin-orbit coupling. Below, we shall argue that these results lead to a contradiction, unless there is any extra effect.

The results of specific heat measurements and muon-spin rotation experiments by Häflicher *et al.* indicate that the whole family of $\text{Li}_2(\text{Pd}_{1-x}\text{Pt}_x)_3\text{B}$ comprises single-gap s-wave superconductors across the entire doping regime [16]. The H - T phase diagram and several superconducting parameters obtained by Peets *et al.* exhibit continuous change as functions of the doping ratio x [17]. Therefore, the pairing symmetries of these compounds are still controversial.

Recently, Shishidou and Oguchi have performed the first-principle calculations in $\text{Li}_2\text{Pd}_3\text{B}$ and $\text{Li}_2\text{Pt}_3\text{B}$, and obtained the Fermi surface structures [10]. Strong spin-orbit coupling results in large splitting of the Fermi surfaces. In each of the spin-orbit split bands, the direction of the spin depends on the momentum. According to their results, every Fermi surface appears to have their partners of the spin-orbit split Fermi surfaces (SFS) in $\text{Li}_2\text{Pd}_3\text{B}$, while some of the Fermi surfaces do not appear to have their partners in $\text{Li}_2\text{Pt}_3\text{B}$ due to stronger spin-orbit coupling, although strictly speaking the relations of the spins and momenta on the SFS are quite complicated.

In this paper, being motivated by the above exper-

imental and theoretical results, we examine phase diagrams of pairing anisotropy in the systems with strong spin-orbit coupling. In particular, we focus on possible drastic changes of the superconductivity when one of the SFS disappears. For example, the experimental and theoretical results mentioned above seem to suggest that a full-gap state changes into a line-node state when the spin-orbit coupling increases and one of the SFS disappears. We abbreviate such a full-gap line-node transition as FLT from now on. Such a behavior may be attributed both to the changes of the electron states and to those of the phonon states. We examine the former possibility in this paper. Although we call such a change a transition, it is not necessarily a phase transition that exhibits a discontinuity at a specific spin-orbit coupling constant. In the real materials, with increasing the coupling constant, the density of states from the Fermi-surfaces without spin-orbit split partners may increase continuously. In this case, averaged physical quantities contributed from both kinds of Fermi-surfaces with and without partners may change continuously.

In Sec. II, we briefly review the formulation used in this paper. The possible forms of the gap functions are shown, and Frigeri *et al.*'s result mentioned above is reproduced. In Sec. III, we derive the expressions of the dimensionless coupling constants and the transition temperatures of the superconductivity on the basis of a model with intra-band pairing interactions and inter-band pair-hopping interactions. We pay special attention to the differences of the two SFS. In Sec. IV, we derive the intra-band pairing interactions and the inter-band pair-hopping interactions from original interactions between electrons with momentum-independent spins. We suppose the charge-charge interaction (CI) and the spin-spin interactions (SI) as original interactions. In Sec. V, we examine two limiting cases, *i.e.*, an equal-band limit and a single-band limit. The latter case occurs when one of the SFS disappears due to stronger spin-orbit coupling. In Sec. VI, in order to illustrate the theory, we examine spherically symmetric systems as examples. Phase diagrams in planes of the coupling constants are shown for several types of interactions. In Sec. VII, we summarize the results and discuss the ternary superconductors. We use the units where $\hbar = 1$ and $k_B = 1$.

II. FORMULATION

First, we examine the Hamiltonian of noninteracting electrons defined by

$$H_0 = \sum_{\mathbf{k}} \begin{pmatrix} c_{\mathbf{k}\uparrow}^\dagger & c_{\mathbf{k}\downarrow}^\dagger \end{pmatrix} (\hat{\epsilon}_{\mathbf{k}} - \mu\sigma_0) \begin{pmatrix} c_{\mathbf{k}\uparrow} \\ c_{\mathbf{k}\downarrow} \end{pmatrix} \quad (1)$$

with

$$\hat{\epsilon}_{\mathbf{k}} = \epsilon_{\mathbf{k}}^0 \sigma_0 - \alpha \hat{\mathbf{g}}(\mathbf{k}) \cdot \boldsymbol{\sigma}, \quad (2)$$

where σ_0 and $\boldsymbol{\sigma}$ are the 2×2 identity matrix and the Pauli matrix, respectively. We suppose the vector func-

tion $\hat{\mathbf{g}}(\mathbf{k})$ that satisfies $\hat{\mathbf{g}}(-\mathbf{k}) = -\hat{\mathbf{g}}(\mathbf{k})$ and $|\hat{\mathbf{g}}(\mathbf{k})| = 1$, and express it as

$$\begin{aligned} \hat{\mathbf{g}}(\mathbf{k}) &= (g_x(\mathbf{k}), g_y(\mathbf{k}), g_z(\mathbf{k})) \\ &= (\sin \bar{\theta}_{\mathbf{k}} \cos \bar{\varphi}_{\mathbf{k}}, \\ &\quad \sin \bar{\theta}_{\mathbf{k}} \sin \bar{\varphi}_{\mathbf{k}}, \cos \bar{\theta}_{\mathbf{k}}) \end{aligned} \quad (3)$$

with the polar coordinates $(\bar{\theta}_{\mathbf{k}}, \bar{\varphi}_{\mathbf{k}})$. We divide the momentum space into two regions $R_{\pm}$, such that

$$\mathbf{k} \in R_{\pm} \Leftrightarrow \pm g_y(\mathbf{k}) > 0,$$

and define unitary matrices by

$$\begin{aligned} U_{\mathbf{k}} &= R_z(\bar{\varphi}_{\mathbf{k}}) R_y(\bar{\theta}_{\mathbf{k}}) \\ &= \begin{pmatrix} e^{-i\frac{\bar{\varphi}_{\mathbf{k}}}{2}} \cos \frac{\bar{\theta}_{\mathbf{k}}}{2} & -e^{-i\frac{\bar{\varphi}_{\mathbf{k}}}{2}} \sin \frac{\bar{\theta}_{\mathbf{k}}}{2} \\ e^{i\frac{\bar{\varphi}_{\mathbf{k}}}{2}} \sin \frac{\bar{\theta}_{\mathbf{k}}}{2} & e^{i\frac{\bar{\varphi}_{\mathbf{k}}}{2}} \cos \frac{\bar{\theta}_{\mathbf{k}}}{2} \end{pmatrix} \end{aligned}$$

$$\begin{aligned} U_{-\mathbf{k}} &= -i R_z(\bar{\varphi}_{-\mathbf{k}}) R_y(\bar{\theta}_{-\mathbf{k}}) \\ &= \begin{pmatrix} -e^{-i\frac{\bar{\varphi}_{\mathbf{k}}}{2}} \sin \frac{\bar{\theta}_{\mathbf{k}}}{2} & e^{-i\frac{\bar{\varphi}_{\mathbf{k}}}{2}} \cos \frac{\bar{\theta}_{\mathbf{k}}}{2} \\ e^{i\frac{\bar{\varphi}_{\mathbf{k}}}{2}} \cos \frac{\bar{\theta}_{\mathbf{k}}}{2} & e^{i\frac{\bar{\varphi}_{\mathbf{k}}}{2}} \sin \frac{\bar{\theta}_{\mathbf{k}}}{2} \end{pmatrix} \end{aligned}$$

for $\mathbf{k} \in R_{+}$. We transform the electron operators $c_{\mathbf{k}\sigma}$ into fermion operators $\tilde{c}_{\mathbf{k}\pm}$ by $(\tilde{c}_{\mathbf{k}+}^\dagger, \tilde{c}_{\mathbf{k}-}^\dagger) = (c_{\mathbf{k}\uparrow}^\dagger, c_{\mathbf{k}\downarrow}^\dagger) U_{\mathbf{k}}$. These transformations are essentially the same as those used in previous papers [1, 2, 8]. Using $U_{\mathbf{k}}$ and $U_{-\mathbf{k}}$, the Hamiltonian H_0 is diagonalized as

$$H_0 = \sum_{s=\pm} \sum_{\mathbf{k} \in R_{+}} \tilde{\xi}_{\mathbf{k}s} \left(\tilde{c}_{\mathbf{k}s}^\dagger \tilde{c}_{\mathbf{k}s} + \tilde{c}_{-\mathbf{k}s}^\dagger \tilde{c}_{-\mathbf{k}s} \right)$$

with $\tilde{\xi}_{\mathbf{k}s} = \epsilon_{\mathbf{k}}^0 - s\alpha - \mu$.

Next, we examine the Cooper-pair operators defined by $\hat{\psi}_{\sigma\sigma'}(\mathbf{k}) \equiv c_{\mathbf{k}\sigma} c_{-\mathbf{k}\sigma'}$ and $\tilde{\psi}_{ss'}(\mathbf{k}) \equiv \tilde{c}_{\mathbf{k}s} \tilde{c}_{-\mathbf{k}s'}$. In terms of the d-vector $\hat{\mathbf{d}}(\mathbf{k}) = (\hat{d}_x(\mathbf{k}), \hat{d}_y(\mathbf{k}), \hat{d}_z(\mathbf{k}))$, and the singlet component $d_0(\mathbf{k})$, the Cooper-pair operators are expressed as

$$\begin{aligned} &\begin{pmatrix} \hat{\psi}_{\uparrow\uparrow}(\mathbf{k}) & \hat{\psi}_{\uparrow\downarrow}(\mathbf{k}) \\ \hat{\psi}_{\downarrow\uparrow}(\mathbf{k}) & \hat{\psi}_{\downarrow\downarrow}(\mathbf{k}) \end{pmatrix} \\ &\equiv \begin{pmatrix} -\hat{d}_x(\mathbf{k}) + i\hat{d}_y(\mathbf{k}) & \hat{d}_z(\mathbf{k}) + \hat{d}_0(\mathbf{k}) \\ \hat{d}_z(\mathbf{k}) - \hat{d}_0(\mathbf{k}) & \hat{d}_x(\mathbf{k}) + i\hat{d}_y(\mathbf{k}) \end{pmatrix}. \end{aligned}$$

The unitary transformations defined above lead to

$$\begin{aligned} \tilde{\psi}_{++}(\mathbf{k}) &= s_{\mathbf{k}} (\hat{\mathbf{g}}(\mathbf{k}) \cdot \hat{\mathbf{d}}(\mathbf{k}) + \hat{d}_0(\mathbf{k})) \\ \tilde{\psi}_{--}(\mathbf{k}) &= s_{\mathbf{k}} (\hat{\mathbf{g}}(\mathbf{k}) \cdot \hat{\mathbf{d}}(\mathbf{k}) - \hat{d}_0(\mathbf{k})) \\ \tilde{\psi}_{+-}(\mathbf{k}) &= \mathbf{g}_{+-}(\mathbf{k}) \cdot \hat{\mathbf{d}}(\mathbf{k}) \\ \tilde{\psi}_{-+}(\mathbf{k}) &= \mathbf{g}_{-+}(\mathbf{k}) \cdot \hat{\mathbf{d}}(\mathbf{k}), \end{aligned} \quad (4)$$

with $s_{\mathbf{k}} = \pm 1$ for $\mathbf{k} \in R_{\pm}$, where we have introduced vectors

$$\begin{aligned} \mathbf{g}_{+-}(\mathbf{k}) &\equiv (-\cos \bar{\theta}_{\mathbf{k}} \cos \bar{\varphi}_{\mathbf{k}} - i \sin \bar{\varphi}_{\mathbf{k}}, \\ &\quad -\cos \bar{\theta}_{\mathbf{k}} \sin \bar{\varphi}_{\mathbf{k}} + i \cos \bar{\varphi}_{\mathbf{k}}, \sin \bar{\theta}_{\mathbf{k}}), \end{aligned} \quad (5)$$

and $\mathbf{g}_{-+}(\mathbf{k}) = -\mathbf{g}_{+-}^*(\mathbf{k})$. All three vectors $\mathbf{g}_{\pm\mp}(\mathbf{k})$ and $\hat{\mathbf{g}}(\mathbf{k})$ are orthogonal to each other.

When $\alpha \gg k_B T_c$, we have $\langle \tilde{\psi}_{\pm\mp}(\mathbf{k}) \rangle = 0$ for any $\mathbf{k}$. This condition, together with Eqs. (4) and (5), immediately results in $\langle \hat{\mathbf{d}}(\mathbf{k}) \rangle \parallel \hat{\mathbf{g}}(\mathbf{k})$, which coincides with the result by Frigeri *et al.* [3]. Hence, we can define a scalar operator $\hat{d}(\mathbf{k})$ such that $\hat{\mathbf{d}}(\mathbf{k}) = \hat{d}(\mathbf{k})\hat{\mathbf{g}}(\mathbf{k})$. Since $\hat{\mathbf{d}}(\mathbf{k})$ and $\hat{\mathbf{g}}(\mathbf{k})$ are of odd parity, the operator $\hat{d}(\mathbf{k})$ is of even parity. In terms of $\hat{d}(\mathbf{k})$ and $\hat{d}_0(\mathbf{k})$, the Cooper-pair operators are rewritten as

$$\tilde{\psi}_{ss}(\mathbf{k}) = s_{\mathbf{k}} (\hat{d}(\mathbf{k}) + s\hat{d}_0(\mathbf{k})). \quad (6)$$

The results of this section do not depend on the form of the pairing interactions.

III. SUPERCONDUCTIVITY

In the weak-coupling theory, the pairing interactions are expressed by

$$H_1 = \frac{1}{N} \sum_{\mathbf{k}, \mathbf{k}'} \sum_{\mu=0}^3 V_{\mu}(\mathbf{k}, \mathbf{k}') \hat{d}_{\mu}^{\dagger}(\mathbf{k}) \hat{d}_{\mu}(\mathbf{k}'), \quad (7)$$

where we have neglected the corrections due to the broken inversion symmetry. When $\alpha \gg k_B T_c$, we can omit the terms that include $\tilde{\psi}_{\pm\mp}$. Hence, Eq. (7) is rewritten as

$$H_1 = \frac{1}{N} \sum_{\mathbf{k}, \mathbf{k}' \in R_+} \sum_{ss'} \Gamma_{ss'}(\mathbf{k}, \mathbf{k}') \tilde{\psi}_{ss}^{\dagger}(\mathbf{k}) \tilde{\psi}_{s's'}(\mathbf{k}'), \quad (8)$$

where

$$\Gamma_{ss'}(\mathbf{k}, \mathbf{k}') = ss' V_{\text{sin}}(\mathbf{k}, \mathbf{k}') + \tilde{V}_{\text{tri}}(\mathbf{k}, \mathbf{k}') \quad (9)$$

for $\mathbf{k}, \mathbf{k}' \in R_+$, and

$$\begin{aligned} V_{\text{sin}}(\mathbf{k}, \mathbf{k}') &= V_0(\mathbf{k}, \mathbf{k}') \\ \tilde{V}_{\text{tri}}(\mathbf{k}, \mathbf{k}') &= \sum_{\mu=1}^3 \hat{g}_{\mu}(\mathbf{k}) V_{\mu}(\mathbf{k}, \mathbf{k}') \hat{g}_{\mu}(\mathbf{k}'). \end{aligned} \quad (10)$$

We define the gap function

$$\Delta_{\mathbf{k}s} = -\frac{1}{N} \sum_{\mathbf{k}' \in R_+} \sum_{s'=\pm} \Gamma_{ss'}(\mathbf{k}, \mathbf{k}') \langle \tilde{\psi}_{s's'}(\mathbf{k}') \rangle \quad (11)$$

and the temperature Green's functions

$$\begin{aligned} \mathcal{G}_s(\mathbf{k}, \tau) &= -\langle T_{\tau} \tilde{c}_{\mathbf{k}s}(\tau) \tilde{c}_{\mathbf{k}s}^{\dagger} \rangle \\ \mathcal{F}_s(\mathbf{k}, \tau) &= -\langle T_{\tau} \tilde{c}_{-\mathbf{k}s}^{\dagger}(\tau) \tilde{c}_{\mathbf{k}s}^{\dagger} \rangle, \end{aligned}$$

with $A(\tau) = e^{\tau H} A e^{-\tau H}$ and $H = H_0 + H_1$. The gap function is written as

$$\Delta_{\mathbf{k}s}^* = \frac{1}{N} \sum_{\mathbf{k}' \in R_+} \sum_{s'=\pm} \Gamma_{ss'}(\mathbf{k}, \mathbf{k}') \mathcal{F}_{s'}(\mathbf{k}', -0).$$

We obtain

$$\begin{aligned} \mathcal{G}_s(\mathbf{k}, \omega_n) &= \frac{i\omega_n + \tilde{\xi}_{\mathbf{k}s}}{(i\omega_n - E_{\mathbf{k}s})(i\omega_n + E_{\mathbf{k}s})} \\ \mathcal{F}_s(\mathbf{k}, \omega_n) &= \frac{\Delta_{\mathbf{k}s}^*}{(i\omega_n - E_{\mathbf{k}s})(i\omega_n + E_{\mathbf{k}s})}, \end{aligned} \quad (12)$$

with the quasi-particle energy

$$E_{\mathbf{k}s} = \sqrt{\tilde{\xi}_{\mathbf{k}s}^2 + |\Delta_{\mathbf{k}s}|^2}, \quad (13)$$

as previous authors have obtained [1, 2, 5, 8]. We obtain the self-consistent equation

$$\Delta_{\mathbf{k}s} = -\frac{1}{N} \sum_{\mathbf{k}' \in R_+} \sum_{s'=\pm} \Gamma_{ss'}(\mathbf{k}, \mathbf{k}') W(E_{\mathbf{k}'s'}) \Delta_{\mathbf{k}'s'}, \quad (14)$$

where $W(E) = \tanh(E/2T)/2E$.

We assume that the pairing interactions exist only between electrons near the Fermi surfaces, not only when the interactions are mediated by phonons, but also when they are mediated by spin and charge fluctuations [8, 18, 19]. This can be taken into account by introducing effective cutoff energies for each vertex function $\Gamma_{ss'}(\mathbf{k}, \mathbf{k}')$. In general, the cutoff energies depend on the positions of the interacting electrons on the Fermi surfaces. In particular, we retain the dependence on the band indexes of the interacting electrons. Therefore, the gap functions are written in the forms

$$\Delta_{\mathbf{k}s} = \Delta_{\mathbf{k}}^{(s)} \theta(\omega_c^{(s)} - |\tilde{\xi}_{\mathbf{k}s}|), \quad (15)$$

where $\hat{\mathbf{k}} = \mathbf{k}/|\mathbf{k}|$, and the pairing interactions are written in the separable forms

$$\Gamma_{ss'}(\mathbf{k}, \mathbf{k}') = \Gamma_{\hat{\mathbf{k}}\hat{\mathbf{k}}'}^{(ss')} \theta(\omega_c^{(s)} - |\tilde{\xi}_{\mathbf{k}s}|) \theta(\omega_c^{(s')} - |\tilde{\xi}_{\mathbf{k}'s'}|). \quad (16)$$

For the pairing interaction mediated by phonons, the cutoff frequencies $\omega_c^{(s)}$ can be replaced with the Debye frequency ω_D , which does not strongly depend on the band index $s = \pm$. For those mediated by electronic fluctuations, they are characteristic energy scales of the fluctuations, which strongly depend on the band index $s = \pm$, because the nesting condition strongly depends on which Fermi surfaces concern. The spin and charge susceptibility have a sharp peak at a nesting vector $\mathbf{q}_0$ that connects the parts of the Fermi surfaces with a better nesting condition. Thus, the pairing interactions mediated by corresponding fluctuations become strong at $\mathbf{q}_0$, within a momentum width comparable to the peak width of the corresponding susceptibility [20]. Since the peak width reflects the difference between the original Fermi surface and that shifted by the nesting vector, the cutoff frequencies $\omega_c^{(s)}$ are energy scales that correspond to the peak width in the momentum space. For example, smaller $\omega_c^{(+)}$ or $\omega_c^{(-)}$ means the critical slowing down of the fluctuations in the proximity to the corresponding

phase transition. Therefore, it is worth examining the influence of the difference of $\omega_c^{(+)}$ and $\omega_c^{(-)}$ on the superconductivity.

We rewrite the gap equation in the above model. Introducing density of states ρ_s defined by

$$\frac{1}{N} \sum_{\mathbf{k}} F(\tilde{\xi}_{\mathbf{k}s}, \hat{\mathbf{k}}) = \int \frac{d\Omega_{\hat{\mathbf{k}}}}{4\pi} \int d\xi \rho_s(\xi, \hat{\mathbf{k}}) F(\xi, \hat{\mathbf{k}}),$$

where $F(\xi, \hat{\mathbf{k}})$ is an arbitrary function, Eq. (14) is written in the form

$$\Delta_{\hat{\mathbf{k}}}^{(s)} = -\frac{1}{2} \sum_{s'=\pm} \int \frac{d\Omega_{\hat{\mathbf{k}}'}}{4\pi} \rho_{s'}(0, \hat{\mathbf{k}}') \Gamma_{\hat{\mathbf{k}}\hat{\mathbf{k}}'}^{(ss')} \times \int_{-\omega_c^{(s')}}^{\omega_c^{(s')}} d\xi W((\xi^2 + |\Delta_{\hat{\mathbf{k}}'}^{(s')}|^2)^{\frac{1}{2}}) \Delta_{\hat{\mathbf{k}}'}^{(s')}.$$

Supposing the second-order phase-transition, the superconducting transition temperature T_c is given by the condition of the first appearance of the nontrivial solution of the eigen equations

$$\Delta_{\hat{\mathbf{k}}}^{(s)} = -\frac{1}{2} \sum_{s'=\pm} \int \frac{d\Omega_{\hat{\mathbf{k}}'}}{4\pi} \rho_{s'}(0, \hat{\mathbf{k}}') \Gamma_{\hat{\mathbf{k}}\hat{\mathbf{k}}'}^{(ss')} \times \ln \frac{2e^{\gamma} \omega_c^{(s')}}{\pi T_c} \Delta_{\hat{\mathbf{k}}'}^{(s')}, \quad (17)$$

where $\gamma = 0.57721 \dots$ is the Euler's constant.

On the basis of Eqs. (15) and (16), we introduce the basis functions

$$\gamma_{\alpha}^{(s)}(\mathbf{k}) = \theta(\omega_c^{(s)} - |\tilde{\xi}_{\mathbf{k}s}|) \gamma_{\alpha}(\hat{\mathbf{k}})$$

that are normalized by

$$\frac{1}{N} \sum_{\mathbf{k}} [\gamma_{\alpha}^{(s)}(\mathbf{k})]^* \gamma_{\alpha'}^{(s)}(\mathbf{k}) = \delta_{\alpha\alpha'}.$$

Here, α and $\gamma_{\alpha}(\hat{\mathbf{k}})$ denote a symmetry index and the corresponding basis function with respect to the direction of $\mathbf{k}$, respectively. Choosing a set of the basis functions that is compatible with the symmetry of the system, the pairing interactions are expressed as

$$V_{\mu}(\mathbf{k}, \mathbf{k}') = \sum_{\alpha} [\gamma_{\alpha}^{(s)}(\mathbf{k})]^* V_{\mu\alpha}^{(ss')} \gamma_{\alpha}^{(s')}(\mathbf{k}'), \quad (18)$$

and

$$\Gamma_{ss'}(\mathbf{k}, \mathbf{k}') = s_{\mathbf{k}} s_{\mathbf{k}'} \sum_{\alpha(\text{even})} [\gamma_{\alpha}^{(s)}(\mathbf{k})]^* \Gamma_{\alpha}^{(ss')} \gamma_{\alpha}^{(s')}(\mathbf{k}').$$

We should note that only α 's of even parity appear in the expansion of $\Gamma_{ss'}$ from Eqs. (9) and (10). With $\tilde{V}_{\alpha}^{(ss')}$ defined by

$$\tilde{V}_{\text{tri}}(\mathbf{k}, \mathbf{k}') = \sum_{\alpha(\text{even})} [\gamma_{\alpha}^{(s)}(\mathbf{k})]^* \tilde{V}_{\alpha}^{(ss')} \gamma_{\alpha}^{(s')}(\mathbf{k}'),$$

we obtain

$$\Gamma_{\alpha}^{(ss')} = s s' V_{0\alpha}^{(ss')} + \tilde{V}_{\alpha}^{(ss')} \quad (19)$$

from Eq. (9). The gap functions are expressed as

$$\Delta_{\mathbf{k}s} = s_{\mathbf{k}} \sum_{\alpha(\text{even})} \Delta_{\alpha}^{(s)} \gamma_{\alpha}^{(s)}(\mathbf{k}). \quad (20)$$

The linearized gap equation (17) is decoupled into a set of equations

$$\Delta_{\alpha}^{(s)} = \sum_{s'=\pm} \lambda_{\alpha}^{(ss')} \ln \frac{2e^{\gamma} \omega_c^{(s')}}{\pi T_{c\alpha}} \Delta_{\alpha}^{(s')},$$

with

$$\lambda_{\alpha}^{(ss')} = -\frac{1}{2} \Gamma_{\alpha}^{(ss')} \rho_{s'}^{(\alpha)}(0) \quad (21)$$

and

$$\rho_{s'}^{(\alpha)}(0) \equiv \int \frac{d\Omega_{\hat{\mathbf{k}}'}}{4\pi} \rho_{s'}(0, \hat{\mathbf{k}}') |\gamma_{\alpha}(\hat{\mathbf{k}}')|^2.$$

Here, $T_{c\alpha}$'s denote the transition temperatures when $\Delta_{\alpha'}^{(s)} \propto \delta_{\alpha'\alpha}$ is assumed. The physical transition temperature, below which there exists a nontrivial solution $\Delta_{\mathbf{k}s} \neq 0$, is given by $T_c = \max_{\alpha} T_{c\alpha}$.

When we restrict ourselves to a symmetry index α that gives the highest $T_{c\alpha}$, we omit the index as $\Delta_s = \Delta_{\alpha}^{(s)}$, $l_s = \ln(2e^{\gamma} \omega_c^{(s)}/\pi T_c)$ and define intra- and inter-band coupling constants by $\lambda_s = \lambda_{\alpha}^{(ss)}$ and $\lambda'_s = \lambda_{\alpha}^{(s,-s)}$. Hence, the linearized gap equation is written as

$$\begin{pmatrix} 1 - \lambda_+ l_+ & -\lambda'_+ l_- \\ -\lambda'_- l_+ & 1 - \lambda_- l_- \end{pmatrix} \begin{pmatrix} \Delta_+ \\ \Delta_- \end{pmatrix} = \begin{pmatrix} 0 \\ 0 \end{pmatrix}. \quad (22)$$

We introduce an arbitrary energy scale ω_c comparable to $\omega_c^{(\pm)}$, and define $\delta_{\pm} \equiv \ln(\omega_c^{(\pm)}/\omega_c)$, and $l \equiv \ln(\omega_c/T)$. We obtain an expression of the transition temperature

$$T_c = \frac{2e^{\gamma}}{\pi} \omega_c e^{-\frac{1}{\Lambda}} \quad (23)$$

with an effective coupling constant

$$\Lambda = \frac{1}{2} \left[\tilde{\lambda}_+ + \tilde{\lambda}_- \pm \sqrt{(\tilde{\lambda}_+ - \tilde{\lambda}_-)^2 + 4\tilde{\lambda}'_+ \tilde{\lambda}'_-} \right], \quad (24)$$

with $\tilde{\lambda}_{\pm} = (\lambda_{\pm} - \delta_{\mp} d_{\lambda})/(1 - \tilde{\delta})$, $\tilde{\lambda}'_{\pm} = \lambda'_{\pm}/(1 - \tilde{\delta})$, and $\tilde{\delta} = \lambda_+ \delta_+ + \lambda_- \delta_- - \delta_+ \delta_- d_{\lambda}$, $d_{\lambda} = \lambda_+ \lambda_- - \lambda'_+ \lambda'_-$. In Eq. (24), we take the sign which gives larger T_c and satisfies the condition that $\Lambda > 0$ and $T_c \ll \omega_c^{(\pm)}$. If we set $\omega_c = \omega_c^{(+)} = \omega_c^{(-)}$, Eq. (24) with + sign is reduced to the expression obtained by Samokhin and Mineev [8]. Defining $p = \{\sqrt{1 + 4r_{\lambda}/\lambda_+ \lambda_- q^2} - 1\}/2$, $q = \lambda_-^{-1} - \lambda_+^{-1} + (1 - r_{\lambda})l_{\omega}$, $r_{\lambda} = \lambda'_+ \lambda'_-/\lambda_+ \lambda_-$, and $l_{\omega} = \ln(\omega_c^{(+)}/\omega_c^{(-)})$, we obtain a compact form

$$\frac{1}{\Lambda} = \frac{1}{1 - r_{\lambda}} \left(\frac{1}{\lambda_{\mp}} \mp pq \right)$$

and $T_c = (2e^\gamma/\pi)\omega_c^{(\pm)} \exp(-1/\Lambda)$.

Figure 1 shows behaviors of the transition temperatures in the presence of the $\pm$ band mixing. $T_{c0}^{(s)}$ denotes the transition temperature of a single s -band with $\lambda'_\pm = 0$. Without losing generality, we have assumed $\lambda_+ > \lambda_-$. Note that the scale of $T_{c0}^{(-)}$ is much smaller than those of $T_{c0}^{(+)}$ and T_c in Fig. 1. It is found that the presence of λ_- , even if it is so small that gives negligibly small $T_{c0}^{(-)}$, remarkably enhances the transition temperature through the inter-band interactions $\lambda'_\pm$. The transition temperature increases as the ratio $\omega_c^{(-)}/\omega_c^{(+)}$ increases. We obtain essentially the same behavior, when $T_{c0}^{(-)}$ is fixed by adjusting λ_- , as shown by the dot-dashed curve in Fig. 1. Therefore, the imbalance of $\omega_c^{(\pm)}$ tends to enhance the transition temperature through the inter-band mixing effect. As argued above, the model with $\omega_c^{(-)} \gtrsim \omega_c^{(+)}$ and $\lambda_- \lesssim \lambda_+$ corresponds to the system in which the nesting condition of the $+$ band Fermi surface is better than that of the $-$ band Fermi surface.

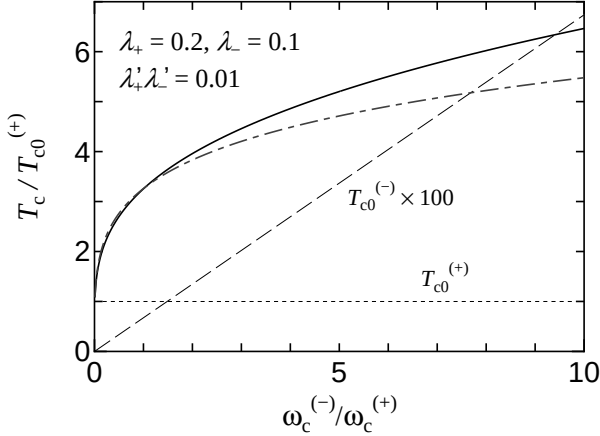


FIG. 1: Transition temperatures as functions of the cutoff energy. The solid and dashed curves show T_c and $T_{c0}^{(-)}$, respectively. As an example, $\lambda_+ = 0.2$, $\lambda_- = 0.1$, $\lambda'_+ \lambda'_- = 0.01$ are assumed. The dot-dash curve shows the result when the ratio $T_{c0}^{(-)}/T_{c0}^{(+)} = 0.007$ is fixed by adjusting λ_- .

IV. PAIRING INTERACTIONS

In this section, we examine the transformation of the original charge-charge and spin-spin interactions into the pairing interactions between the electrons on the SFS. We examine the interactions of the form

$$H_1 = H_{1c} + H_{1z} + H_{1\perp}, \quad (25)$$

with the charge-charge interaction (CI)

$$H_{1c} = \sum_{i,j} V_{ij}^c n_i n_j, \quad (26)$$

the Ising-type interaction

$$H_{1z} = \sum_{i,j} J_{ij}^z S_i^z S_j^z, \quad (27)$$

and the planar spin interaction

$$H_{1\perp} = \sum_{i,j} J_{ij}^\perp (S_i^x S_j^x + S_i^y S_j^y). \quad (28)$$

Here, $n_i = \sum_\sigma c_{i\sigma}^\dagger c_{i\sigma}$ and $\mathbf{S}_i = \frac{1}{2} \sum_{\sigma_1 \sigma_2} c_{i\sigma_1}^\dagger \boldsymbol{\sigma}_{\sigma_1 \sigma_2} c_{i\sigma_2}$. The CI can be derived as an effective interaction mediated by phonons and charge fluctuations, while the SI can be derived as that mediated by spin fluctuations, which includes the kinetic exchange and super-exchange interactions. We have ignored the broken inversion symmetry in the interactions, although it might give rise to some interesting effect. We define $V^z \equiv J^z$ and $V^\perp \equiv J^\perp$ for simplicity of the notation. The above interactions give rise to the pairing interactions as

$$\begin{aligned} H_{1c} &= \frac{1}{N} \sum_{\mathbf{k}\mathbf{k}'\sigma\sigma'} V_c(\mathbf{k}, \mathbf{k}') \hat{\psi}_{\sigma\sigma'}^\dagger(\mathbf{k}) \hat{\psi}_{\sigma\sigma'}(\mathbf{k}') \\ H_{1z} &= \frac{1}{4N} \sum_{\mathbf{k}\mathbf{k}'\sigma\sigma'} \sigma\sigma' J_z(\mathbf{k}, \mathbf{k}') \hat{\psi}_{\sigma\sigma'}^\dagger(\mathbf{k}) \hat{\psi}_{\sigma\sigma'}(\mathbf{k}') \\ H_{1\perp} &= -\frac{1}{2N} \sum_{\mathbf{k}\mathbf{k}'\sigma} J_\perp(\mathbf{k}, \mathbf{k}') \hat{\psi}_{\sigma-\sigma}^\dagger(\mathbf{k}) \hat{\psi}_{\sigma-\sigma}(\mathbf{k}') \end{aligned} \quad (29)$$

within the BCS approximation, where we have defined

$$V_q^X \equiv \sum_{\mathbf{R}_{ij}} e^{-i\mathbf{q} \cdot \mathbf{R}_{ij}} V_{ij}^X \quad (X = c, z, \text{ and } \perp),$$

$V_c(\mathbf{k}, \mathbf{k}') = V_{\mathbf{k}-\mathbf{k}'}^c$, $V_z(\mathbf{k}, \mathbf{k}') = V_{\mathbf{k}-\mathbf{k}'}^z$, and $V_\perp(\mathbf{k}, \mathbf{k}') = V_{\mathbf{k}+\mathbf{k}'}^\perp$. The α -components $V_{X\alpha}^{(ss')}$ are defined by the equations analogous to Eq. (18). Rewriting Eq. (29) into the forms of Eqs. (8), (9), and (10), we obtain the α -components of the singlet and triplet coupling constants

$$\begin{aligned} V_{0\alpha}^{(ss')} &= 2V_{c\alpha}^{(ss')} - \frac{1}{2} J_{z\alpha}^{(ss')} - J_{\perp\alpha}^{(ss')} \\ \tilde{V}_\alpha^{(ss')} &= \sum_{\alpha'(\text{odd})} \left[2g_{2\alpha\alpha'}^{(ss')} V_{c\alpha'}^{(ss')} + \frac{1}{2} \bar{g}_{2\alpha\alpha'}^{(ss')} J_{z\alpha'}^{(ss')} \right. \\ &\quad \left. - g_{2z\alpha\alpha'}^{(ss')} J_{\perp\alpha'}^{(ss')} \right]. \end{aligned}$$

Therefore, we obtain the transformation rule

$$\Gamma_\alpha^{(ss')} = \sum_{\alpha' X} \mathcal{T}_{X\alpha\alpha'}^{(ss')} V_{X\alpha'}^{(ss')}, \quad (30)$$

where

$$\begin{aligned} \mathcal{T}_{c\alpha\alpha'}^{(ss')} &= 2ss'\delta_{\alpha\alpha'} + 2g_{2\alpha\alpha'}^{(ss')} \\ \mathcal{T}_{z\alpha\alpha'}^{(ss')} &= -\frac{ss'}{2}\delta_{\alpha\alpha'} + \frac{1}{2}\bar{g}_{2\alpha\alpha'}^{(ss')} \\ \mathcal{T}_{\perp\alpha\alpha'}^{(ss')} &= -ss'\delta_{\alpha\alpha'} - g_{2z\alpha\alpha'}^{(ss')}, \end{aligned} \quad (31)$$

and

$$\begin{aligned} g_{2\alpha\alpha'}^{(ss')} &= g_{2x\alpha\alpha'}^{(ss')} + g_{2y\alpha\alpha'}^{(ss')} + g_{2z\alpha\alpha'}^{(ss')} \\ \bar{g}_{2\alpha\alpha'}^{(ss')} &= g_{2x\alpha\alpha'}^{(ss')} + g_{2y\alpha\alpha'}^{(ss')} - g_{2z\alpha\alpha'}^{(ss')} \end{aligned} \quad (32)$$

with $g_{2\nu\alpha\alpha'}^{(ss')} = g_{\nu\alpha\alpha'}^{(s)} g_{\nu\alpha'\alpha}^{(s')}$ and

$$g_{\nu\alpha\alpha'}^{(s)} = \frac{1}{N} \sum_{\mathbf{k}} \gamma_{\alpha}^{(s)}(\mathbf{k}) \hat{g}_{\nu}(\mathbf{k}) [\gamma_{\alpha'}^{(s)}(\mathbf{k})]^*.$$

In particular, for isotropic spin interaction $J_{ij}^z = J_{ij}^{\perp} \equiv J_{ij}$, we obtain

$$\begin{aligned} V_{0\alpha}^{(ss')} &= 2V_{c\alpha}^{(ss')} - \frac{3}{2}J_{\alpha}^{(ss')} \\ \tilde{V}_{\alpha}^{(ss')} &= \sum_{\alpha'(\text{odd})} g_{2\alpha\alpha'}^{(ss')} \left\{ 2V_{c\alpha'}^{(ss')} + \frac{1}{2}J_{\alpha'}^{(ss')} \right\}. \end{aligned} \quad (33)$$

In the model with a strong on-site Coulomb interaction U , the interaction

$$H_1 = \sum_{(i,j)} J(\mathbf{S}_i \cdot \mathbf{S}_j - \frac{1}{4}n_i n_j) \quad (34)$$

is derived in the second-order perturbation of the hopping integral t with $t \ll U$. This form corresponds to the present model Eq. (25) with $J_{ij}^z = J_{ij}^{\perp} \equiv J_{ij}$ and $V_{ij}^c = -J_{ij}/4$. Therefore, from Eq. (33), we obtain

$$\begin{aligned} V_{0\alpha}^{(ss')} &= -2J_{\alpha}^{(ss')} \\ \tilde{V}_{\alpha}^{(ss')} &= 0. \end{aligned}$$

Since Eq. (34) does not have triplet interactions, any effect due to the singlet-triplet mixing that we will describe below does not occur.

In the above equations, α must be of even parity as mentioned above. Therefore, α' must be of odd parity in the second terms of Eqs. (31), because $\hat{\mathbf{g}}(\mathbf{k})$ is an odd function. The pairing interactions $V_{X\alpha'}^{(ss')}$ with odd (even) α' contribute to the gap function of even α through the triplet (singlet) components $\tilde{V}_{\text{tri}}$ (V_{sin}). For example, in a spherically symmetric system, p-wave interaction contributes to both s-wave and d-wave pairing, while s-wave and d-wave pairing do not contribute to each other.

V. TWO LIMITING CASES

In this section, we compare the results of two opposite limiting cases: an equal-band limit and a single-band limit, which are defined below.

A. The equal-band limit

We define the equal-band limit by the conditions for the densities of states

$$\rho_+^{(\alpha)}(0) = \rho_-^{(\alpha)}(0) \equiv \rho_F, \quad (35)$$

and interaction parameters $V_{0\alpha}^{(\pm\pm)} = V_{0\alpha}^{(\pm\mp)} \equiv V_{\alpha}^{\text{sin}}$, $\tilde{V}_{\alpha}^{(\pm\pm)} = \tilde{V}_{\alpha}^{(\pm\mp)} \equiv \tilde{V}_{\alpha}^{\text{tri}}$, and $\omega_c^{(+)} = \omega_c^{(-)}$, which are independent of the band indexes, while the SFS are displaced in momentum space because we have set $\langle \hat{\psi}_{\pm\mp}(\mathbf{k}) \rangle = 0$. We define $\lambda_{\alpha}^{\text{sin}} = -\frac{1}{2}V_{\alpha}^{\text{sin}}\rho_F$ and $\lambda_{\alpha}^{\text{tri}} = -\frac{1}{2}\tilde{V}_{\alpha}^{\text{tri}}\rho_F$. Then, we obtain $\lambda_{\alpha}^{(ss')} = ss'\lambda_{\alpha}^{\text{sin}} + \lambda_{\alpha}^{\text{tri}}$, *i.e.*,

$$\begin{aligned} \lambda_{\alpha} &\equiv \lambda_+ = \lambda_- = \lambda_{\alpha}^{\text{sin}} + \lambda_{\alpha}^{\text{tri}} \\ \lambda'_{\alpha} &\equiv \lambda'_+ = \lambda'_- = -\lambda_{\alpha}^{\text{sin}} + \lambda_{\alpha}^{\text{tri}}. \end{aligned}$$

Setting $\omega_c = \omega_c^{(\pm)}$ in Eq. (24), we obtain

$$\Lambda_{\alpha} = \lambda_{\alpha} \pm |\lambda'_{\alpha}| = \begin{cases} 2\lambda_{\alpha}^{\text{sin}} \\ 2\lambda_{\alpha}^{\text{tri}} \end{cases}, \quad (36)$$

the larger positive one of which is the physical solution. For $\Lambda_{\alpha} = 2\lambda_{\alpha}^{\text{sin}}$ and $2\lambda_{\alpha}^{\text{tri}}$, the gap function becomes

$$\begin{pmatrix} \Delta_{\alpha}^{(+)} \\ \Delta_{\alpha}^{(-)} \end{pmatrix} = \begin{pmatrix} \Delta_{\alpha} \\ -\Delta_{\alpha} \end{pmatrix} \quad \text{and} \quad \begin{pmatrix} \Delta_{\alpha} \\ \Delta_{\alpha} \end{pmatrix},$$

respectively. Therefore, in this ideal case, the gap function becomes purely singlet or triplet, respectively.

B. The single-band limit

The single-band limit is defined so that only one of the spin-orbit split bands has a Fermi-surface, which is expressed as

$$\rho_+^{(\alpha)}(0) = \rho_F \quad \text{and} \quad \rho_-^{(\alpha)}(0) = 0. \quad (37)$$

The limit can be used as a theoretical model for some of the Fermi surfaces in $\text{Li}_2\text{Pt}_3\text{B}$. Since $\lambda_- = \lambda'_- = 0$ and $\Delta_- = 0$, the linearized gap equation Eq. (22) becomes $\Delta_+ = \lambda_+ l_+ \Delta_+$. Therefore, we obtain

$$\Lambda_{\alpha} = \lambda_{\alpha}^{(++)} = \lambda_{\alpha}^{\text{sin}} + \lambda_{\alpha}^{\text{tri}}, \quad (38)$$

with $\omega_c = \omega_c^{(+)}$. The gap function becomes

$$\begin{pmatrix} \Delta_{\alpha}^{(+)} \\ \Delta_{\alpha}^{(-)} \end{pmatrix} = \begin{pmatrix} \Delta_{\alpha} \\ 0 \end{pmatrix}.$$

Hence, we obtain $\mathcal{F}_-(\mathbf{k}, \omega_n) = 0$ and $|\langle \hat{d}(\mathbf{k}) \rangle| = |\langle \hat{d}_0(\mathbf{k}) \rangle|$ from Eqs. (6) and (12), where $|\dots|$ is to get rid of the arbitrary phase factors. In contrast to the equal-band limit, the amplitudes of the spin-singlet and triplet components coincide.

Thus, the properties of the superconductivity are completely different in the two limits. The disappearance of one of the SFS causes a drastic change in the transition temperature and the gap structure. This might explain the difference between the experimental results in $\text{Li}_2\text{Pd}_3\text{B}$ and $\text{Li}_2\text{Pt}_3\text{B}$ discussed in Sec. I. For example, the full-gap structure may change into a gap structure with line nodes, when the spin-orbit coupling α increases. We shall illustrate it in the following sections.

VI. PHASE DIAGRAMS

We apply the present theory to several specific models. As an example, we suppose that the system has spherically symmetric Fermi surfaces, and $\hat{\mathbf{g}}(\mathbf{k}) = \hat{\mathbf{k}}$. We set $\alpha = (l, m)$ and define the spherical harmonic functions by

$$Y_{lm}(\hat{\mathbf{k}}) = Y_{lm}(\theta_{\hat{\mathbf{k}}}, \varphi_{\hat{\mathbf{k}}}) = P_l^m(\cos \theta_{\hat{\mathbf{k}}}) e^{im\varphi_{\hat{\mathbf{k}}}},$$

where $\theta_{\hat{\mathbf{k}}}$ and $\varphi_{\hat{\mathbf{k}}}$ denote the polar angles to express the direction of $\hat{\mathbf{k}}$, and $P_l^m(w)$ denotes the Legendre polynomial. The basis functions are written as

$$\gamma_{lm}^{(s)}(\mathbf{k}) = C_{lm}^{(s)} \theta(\omega_c^{(s)} - |\xi_{\mathbf{k}s}|) Y_{lm}(\hat{\mathbf{k}})$$

with the normalization factor $C_{lm}^{(s)}$. In the expansions of the interactions, we assume that $V_{X(lm)}^{(ss')} = V_{Xl}$, and retain the terms up to $l = 2$, for simplicity. The coefficients $g_{\nu(lm)(l'm')}^{(ss')}$ can be calculated straightforwardly, for example, as $g_{2z(0,0)(1,0)}^{(ss')} = g_{2z(1,0)(0,0)}^{(ss')} = 1/3$, and so on.

In this section, we examine the two limiting cases defined in the previous section: the equal-band limit and the single-band limit. The former limit is a simplified model of the system in which both of the SFS exist (case (i)), while the latter limit corresponds to the system in which only one of the spin-orbit split bands has the Fermi-surface (case (ii)).

A. Charge-charge interaction

In the system with the CI defined by Eq. (26), we obtain

$$\begin{aligned} \Gamma_{00}^{(ss')} &= 2ss'V_{c0} + 2V_{c1} \\ \Gamma_{2m}^{(ss')} &= 2ss'V_{c2} + \frac{4}{5}V_{c1} \end{aligned}$$

with $m = \pm 2, \pm 1, 0$. Therefore, in the equal-band limit, we obtain

$$\begin{aligned} \lambda_{00} &= \lambda_{c0} + \lambda_{c1}, & \lambda'_{00} &= -\lambda_{c0} + \lambda_{c1}, \\ \lambda_{2m} &= \lambda_{c2} + \frac{2}{5}\lambda_{c1}, & \lambda'_{2m} &= -\lambda_{c2} + \frac{2}{5}\lambda_{c1}, \end{aligned} \quad (39)$$

with $\lambda_{cl} = -V_{cl}\rho_F$. Similar results, except the terms including λ_{c2} , have been obtained by Samokhin and Mineev [8]. The gap function of the s-wave state has a full-gap structure, while those of the d-wave states have line nodes. In the present isotropic model, the transition temperatures of the d-wave pairing are degenerate with respect to m , and a d-wave state expressed by the linear combination of those degenerate states occurs below T_c . By minimizing the free energy, we obtain a d-wave state with a full-gap structure, but this is an artifact due to the isotropy of the model. Taking into account the anisotropy that exists in real crystal systems the degeneracy is lifted, and some of the solutions with different

m 's have the highest T_c . Therefore, considering the reality, we ought to regard the d-wave states as line-node states at least near the transition temperature, while at low temperatures the order parameters with different m 's can be mixed and the full-gap state may occur. From Eqs. (36) and (39), we obtain

$$\begin{aligned} \Lambda_0 &= \max(2\lambda_{c0}, 2\lambda_{c1}, 0) \\ \Lambda_2 &= \max(2\lambda_{c2}, 4\lambda_{c1}/5, 0). \end{aligned} \quad (40)$$

Hence, the resultant coupling constant is expressed as

$$\Lambda = \max(2\lambda_{c0}, 2\lambda_{c2}, 2\lambda_{c1}, 0), \quad (41)$$

which gives the phase diagram shown in Fig. 2. The phase diagrams in this paper are not those at $T = 0$, but the diagrams of the phases that give T_c . Successive transitions to other superconducting phases may occur below T_c .

It is found from Eqs. (40) and (41) that when the even-parity pairing is induced by the spin-triplet pairing, it will have the s-wave symmetry rather than the d-wave symmetry, because $2\lambda_{c1} > 4\lambda_{c1}/5$ for $\lambda_{c1} > 0$. While the p-wave attractive interaction contributes to both the s-wave pairing and the d-wave pairing, the contribution to the s-wave pairing is larger by the factor 5/2. Consequently, as shown in Fig. 2, when the s-wave and d-wave pairing interactions λ_{c0} and λ_{c2} are weak or repulsive, the p-wave pairing interaction induces the s-wave superconductivity. Such an s-wave state has a full-gap structure like the conventional s-wave state, but is at the same time purely spin-triplet state that has the d-vector $\langle \hat{\mathbf{d}}(\mathbf{k}) \rangle = \langle \hat{\mathbf{d}}(\mathbf{k}) \rangle \hat{\mathbf{g}}(\mathbf{k})$ with an even parity amplitude $\langle \hat{\mathbf{d}}(\mathbf{k}) \rangle$. The gap function becomes $\Delta_{\mathbf{k}s} = -2V_{c1}s_{\mathbf{k}}\langle \hat{\mathbf{d}}(\mathbf{k}) \rangle \propto s_{\mathbf{k}}\theta(\omega_c^{(s)} - |\xi_{\mathbf{k}}^{(s)}|)$, which does not have nodes on the Fermi-surface but has the phase factor $s_{\mathbf{k}}$. The energy gaps of the quasi-particle energies $E_{\mathbf{k}\pm}$ become constants $|\Delta_{(0,0)}^{\pm}|$ independent of $\hat{\mathbf{k}}$, from Eqs. (13) and (20). The s-wave spin-triplet order is suggested in $\text{Li}_2\text{Pd}_3\text{B}$ and $\text{Li}_2\text{Pt}_3\text{B}$ by Yuan *et al.* [15]. Interestingly, however strong the repulsive spin-singlet interaction is, weaker attractive spin-triplet interaction could cause the cancellation effect between the intra- and inter-band interactions. On the other hand, in Fig. 2, the d-wave phase in the upper area and s-wave phase in the right area are conventional pure spin-singlet phases induced by d-wave and s-wave pairing interactions, respectively. Away from the equal-band limit, the mixing of spin-singlet and triplet states occurs.

In the single band limit, the effective coupling constant becomes

$$\Lambda = \max(\Lambda_0, \Lambda_2, 0), \quad (42)$$

where $\Lambda_0 = \lambda_{c0} + \lambda_{c1}$ and $\Lambda_2 = \lambda_{2m} = \lambda_{c2} + \frac{2}{5}\lambda_{c1}$, which gives the phase diagram shown in Fig. 3. In both the d-wave and s-wave phases, the singlet-triplet mixing occurs. It is found that the p-wave spin-triplet pairing

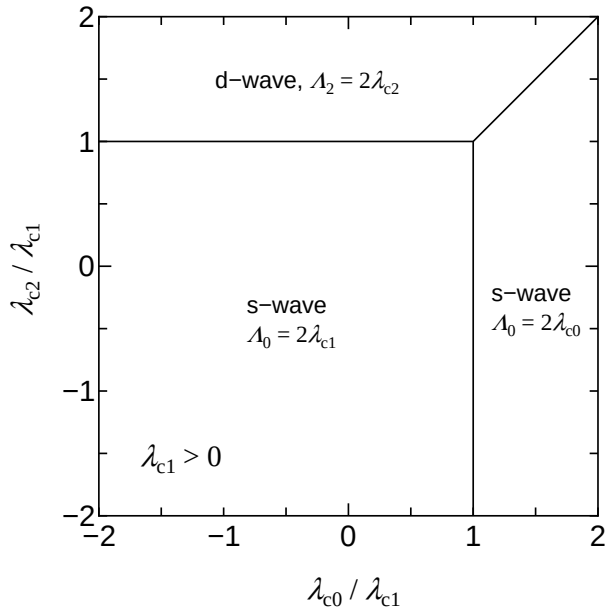


FIG. 2: Phase diagram of the system with the CI, when both of the SFS exist. The spin-triplet interaction is assumed to be attractive.

interaction stabilizes both the d-wave and s-wave phases, but in contrast to the equal band limit, the superconductivity is suppressed, where both of the d-wave and s-wave interactions are repulsive and strong enough.

Figure 4 shows the transitions when one of the SFS disappears. In the gray area, the s-wave full-gap state changes into the d-wave state. Since the d-wave state can be regarded as a line-node state as argued above, the transition in this area is a kind of the FLT. This result may explain the observations in $\text{Li}_2\text{Pd}_3\text{B}$ and $\text{Li}_2\text{Pt}_3\text{B}$ as discussed in Sec. I. In this case, the initial state of the transition is the s-wave spin-triplet state, and the final state is the d-wave state with both spin-singlet and triplet components. The conventional s-wave spin-singlet state can not be the initial state that changes into the final d-wave state, as shown in Fig. 4. This result is roughly interpreted as follows. For the d-wave state to occur as the final state in the single-band limit, the s-wave interaction needs to be weak or repulsive. Therefore, if the s-wave state occurs as the initial state for the same values of the coupling constants, it must be a spin-triplet state induced by the p-wave interaction, rather than a spin-singlet state induced by the s-wave interaction. This interpretation is not a rigorous proof, but verified by Eqs. (41) and (42) and Fig. 4. In the most part of the gray area, the s-wave interaction is repulsive ($\lambda_{c0} < 0$), while the p-wave and d-wave interactions are attractive and the former is stronger than the latter ($0 < \lambda_{c2} < \lambda_{c1}$). These conditions are likely to be satisfied in real materials in which both the screened short-range Coulomb repulsion and phonon mediated pairing

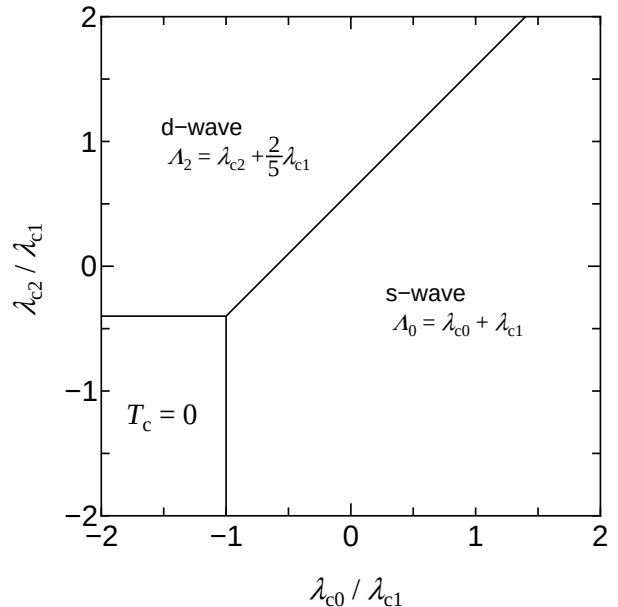


FIG. 3: Phase diagram of the system with the CI, when only one of the spin-orbit split bands has a Fermi-surface. The spin-triplet interaction is assumed to be attractive.

interactions are strong.

Figure 5 shows the transitions in case that the p-wave component of the interaction is repulsive, which might be unlikely if we suppose phonon mediated pairing interaction as the CI [21]. In the gray area, the s-wave full-gap state changes into the d-wave state. In contrast to the previous case, the initial s-wave state is of spin-singlet pairing.

B. Spin-spin interactions

Next, we examine the phase diagrams and the transitions of the systems with the SI H_{z1} and $H_{\perp 1}$ of Eqs. (27) and (28). In this type of interactions, anisotropies of interactions in the spin space play an essential role. Depending on the anisotropy and the sign of the interactions, the transition from the full-gap state to the line-node state (FLT) can occur.

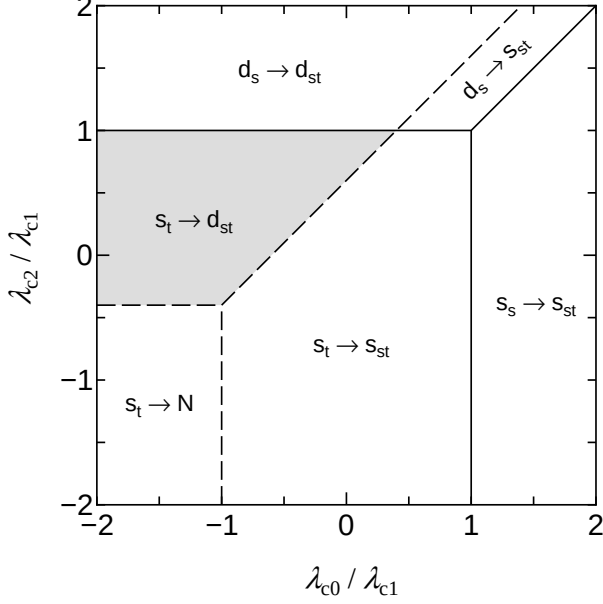


FIG. 4: Superposition of the phase diagrams Figs. 2 and 3 to show the transition when one of the SFS disappears due to increase of the spin-orbit coupling. The spin-triplet interaction is assumed to be attractive ($\lambda_{c1} > 0$). The notation “a $\rightarrow$ b” means the transition from the phase “a” to the phase “b”, where d, s, and N mean d- and s-wave superconducting phases, and the normal phase, respectively. The suffixes s, t, and st mean the spin-singlet, triplet, and singlet-triplet mixed states, respectively. For example, “s_t $\rightarrow$ d_{st}” means the transition from the s-wave spin-triplet state to the d-wave state with both spin-singlet and triplet components.

1. Ising-type interaction

In the system with only Ising-type interaction Eq. (27), we obtain

$$\begin{aligned}\Gamma_{00}^{(ss')} &= -\frac{1}{2}ss'J_{z0} + \frac{1}{6}J_{z1} \\ \Gamma_{20}^{(ss')} &= -\frac{1}{2}ss'J_{z2} - \frac{1}{15}J_{z1} \\ \Gamma_{2,\pm1}^{(ss')} &= -\frac{1}{2}ss'J_{z2} \\ \Gamma_{2,\pm2}^{(ss')} &= -\frac{1}{2}ss'J_{z2} + \frac{1}{5}J_{z1}.\end{aligned}$$

(i) In the equal-band limit, we obtain

$$\begin{aligned}\lambda_{00} &= \lambda_{z0} - \frac{1}{3}\lambda_{z1}, & \lambda'_{00} &= -\lambda_{z0} - \frac{1}{3}\lambda_{z1}, \\ \lambda_{20} &= \lambda_{z2} + \frac{2}{15}\lambda_{z1}, & \lambda'_{20} &= -\lambda_{z2} + \frac{2}{15}\lambda_{z1}, \\ \lambda_{2\pm1} &= \lambda_{z2}, & \lambda'_{2\pm1} &= -\lambda_{z2}, \\ \lambda_{2\pm2} &= \lambda_{z2} - \frac{4}{5}\lambda_{z1}, & \lambda'_{2\pm2} &= -\lambda_{z2} - \frac{4}{5}\lambda_{z1},\end{aligned}\quad (43)$$

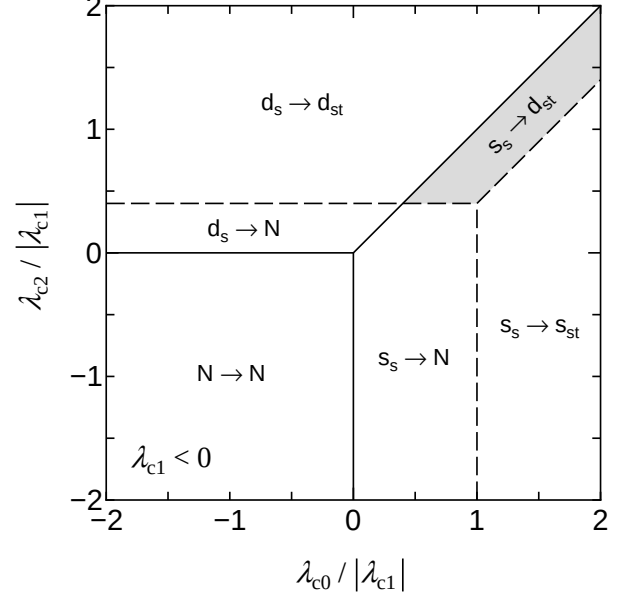


FIG. 5: Transitions when the interaction is of the charge-charge type and the p-wave component is repulsive. The legends are the same as those in Fig. 4.

with $\lambda_{zl} = \frac{1}{4}J_{zl}\rho_F$. Hence, we obtain

$$\begin{aligned}\Lambda_0 &= \max(2\lambda_{z0}, -\frac{2}{3}\lambda_{z1}, 0), \\ \Lambda_{20} &= \max(2\lambda_{z2}, \frac{4}{15}\lambda_{z1}, 0), \\ \Lambda_{2,\pm1} &= \max(2\lambda_{z2}, 0), \\ \Lambda_{2,\pm2} &= \max(2\lambda_{z2}, -\frac{8}{5}\lambda_{z1}, 0),\end{aligned}\quad (44)$$

and

$$\Lambda = \max(2\lambda_{z0}, 2\lambda_{z2}, -\frac{8}{5}\lambda_{z1}, \frac{4}{15}\lambda_{z1}, 0). \quad (45)$$

Interestingly, the *repulsive* p-wave spin-triplet interaction stabilizes both the d-wave spin-triplet state with $(l, m) = (2, \pm 2)$ and the s-wave spin-triplet state. However, because of the numerical factors in front of λ_{z1} , the former overcomes the latter. (ii) In the single-band limit, we obtain

$$\begin{aligned}\Lambda_0 &= \lambda_{z0} - \frac{1}{3}\lambda_{z1}, \\ \Lambda_{20} &= \lambda_{z2} + \frac{2}{15}\lambda_{z1}, \\ \Lambda_{2,\pm1} &= \lambda_{z2}, \\ \Lambda_{2,\pm2} &= \lambda_{z2} - \frac{4}{5}\lambda_{z1}.\end{aligned}\quad (46)$$

The resultant coupling constant is

$$\Lambda = \max(\Lambda_0, \Lambda_{20}, \Lambda_{2,\pm1}, \Lambda_{2,\pm2}, 0). \quad (47)$$

2. Planar spin interaction

In the system with only planar spin interaction Eq. (28), we obtain

$$\begin{aligned}\Gamma_{00}^{(ss')} &= -ss'J_{\perp 0} + \frac{1}{3}J_{\perp 1}, \\ \Gamma_{20}^{(ss')} &= -ss'J_{\perp 2} + \frac{4}{15}J_{\perp 1}, \\ \Gamma_{2,\pm 1}^{(ss')} &= -ss'J_{\perp 2} + \frac{1}{5}J_{\perp 1}, \\ \Gamma_{2,\pm 2}^{(ss')} &= -ss'J_{\perp 2}.\end{aligned}$$

(i) In the equal-band limit, we obtain

$$\begin{aligned}\lambda_{00} &= \lambda_{\perp 0} - \frac{1}{3}\lambda_{\perp 1}, & \lambda'_{00} &= -\lambda_{\perp 0} - \frac{1}{3}\lambda_{\perp 1}, \\ \lambda_{20} &= \lambda_{\perp 2} - \frac{4}{15}\lambda_{\perp 1}, & \lambda'_{20} &= -\lambda_{\perp 2} - \frac{4}{15}\lambda_{\perp 1}, \\ \lambda_{2\pm 1} &= \lambda_{\perp 2} - \frac{1}{5}\lambda_{\perp 1}, & \lambda'_{2\pm 1} &= -\lambda_{\perp 2} - \frac{1}{5}\lambda_{\perp 1}, \\ \lambda_{2\pm 2} &= \lambda_{\perp 2}, & \lambda'_{2\pm 2} &= -\lambda_{\perp 2},\end{aligned}$$

with $\lambda_{\perp l} = \frac{1}{2}J_{\perp l}\rho_F$. Hence, we obtain

$$\begin{aligned}\Lambda_0 &= \max(2\lambda_{\perp 0}, -\frac{2}{3}\lambda_{\perp 1}, 0), \\ \Lambda_{20} &= \max(2\lambda_{\perp 2}, -\frac{8}{15}\lambda_{\perp 1}, 0), \\ \Lambda_{2,\pm 1} &= \max(2\lambda_{\perp 2}, -\frac{2}{5}\lambda_{\perp 1}, 0), \\ \Lambda_{2,\pm 2} &= \max(2\lambda_{\perp 2}, 0),\end{aligned}$$

and

$$\Lambda = \max(2\lambda_{\perp 0}, 2\lambda_{\perp 2}, -\frac{2}{3}\lambda_{\perp 1}, 0).$$

(ii) In the single-band limit, we obtain

$$\begin{aligned}\Lambda_0 &= \lambda_{\perp 0} - \frac{1}{3}\lambda_{\perp 1}, \\ \Lambda_{20} &= \lambda_{\perp 2} - \frac{4}{15}\lambda_{\perp 1}, \\ \Lambda_{2,\pm 1} &= \lambda_{\perp 2} - \frac{1}{5}\lambda_{\perp 1}, \\ \Lambda_{2,\pm 2} &= \lambda_{\perp 2}.\end{aligned}$$

The resultant coupling constant is the maximum positive one as given by Eq. (47).

3. Isotropic spin interaction

Lastly, in the system with isotropic spin interaction $J_{ij}^z = J_{ij}^{\perp} \equiv J_{ij}$, we obtain

$$\begin{aligned}\Gamma_0^{(ss')} &= -ss'\frac{3}{2}J_0 + \frac{1}{2}J_1, \\ \Gamma_2^{(ss')} &= -ss'\frac{3}{2}J_2 + \frac{1}{5}J_1.\end{aligned}$$

(i) In the equal-band limit, we obtain

$$\begin{aligned}\lambda_0 &= \lambda_0 - \frac{1}{3}\lambda_1, & \lambda'_0 &= -\lambda_0 - \frac{1}{3}\lambda_1, \\ \lambda_2 &= \lambda_2 - \frac{2}{15}\lambda_1, & \lambda'_2 &= -\lambda_2 - \frac{2}{15}\lambda_1.\end{aligned}$$

with $\lambda_l = \frac{3}{4}J_l\rho_F$. Hence, we obtain

$$\begin{aligned}\Lambda_0 &= \max(2\lambda_0, -\frac{2}{3}\lambda_1, 0), \\ \Lambda_2 &= \max(2\lambda_2, -\frac{4}{15}\lambda_1, 0),\end{aligned}$$

and

$$\Lambda = \max(2\lambda_0, 2\lambda_2, -\frac{2}{3}\lambda_1, 0). \quad (48)$$

(ii) In the single-band limit, we obtain

$$\begin{aligned}\Lambda_0 &= \lambda_0 - \frac{1}{3}\lambda_1, \\ \Lambda_2 &= \lambda_2 - \frac{2}{15}\lambda_1,\end{aligned}$$

and

$$\Lambda = \max(\lambda_0 - \frac{1}{3}\lambda_1, \lambda_2 - \frac{2}{15}\lambda_1, 0). \quad (49)$$

4. Phase diagrams and the transitions

In this subsection, we examine the phase diagrams of the systems with SI. Figures 6 - 11 show the phase diagrams of the systems with various types of the SI (see Table I). In each figure, two phase diagrams are superposed in the way shown in Figs. 2 - 4 for the CI. The solid lines show the phase boundaries for case (i), and the broken lines and the texts in the brackets show the phase boundaries and the symmetries of the phases for case (ii). As explained in the caption of Fig. 4, the notation “a $\rightarrow$ b” means the transitions from the phase “a” to the phase “b”, when one of the SFS disappears (case (i) $\rightarrow$ case (ii)). In addition to the characters “s”, “d”, and “N”, we have defined the notation “2m” that means the d-wave state with $\Delta \propto Y_{2m}$.

In case (i), anomalous even-parity (s- and d-wave) spin-triplet superconducting phases occur, where both the s- and d-wave components of the interactions are repulsive. The Ising-type interactions induce the d-wave spin-triplet states with different m for either sign of the p-wave component (Figs. 6 and 7), in contrast to the CI. The magnetically mediated pairing interactions could also induce the s-wave spin-triplet states, when the interaction is planar or isotropic and their p-wave component is repulsive (Figs. 8, 9, 10, 11). These results are quite different from that in the system with the CI, in which s-wave spin-triplet state occurs only when the p-wave component of the interaction is attractive. These differences are explained as follows. When the singlet interactions are repulsive, only the triplet p-wave interaction contributes to the even-parity state through the mixing effect due to the spin-orbit coupling. Depending on the sign of the second terms of the matrix elements $\mathcal{T}_{X\alpha\alpha'}^{(ss')}$ ($X = c, z, \perp$) defined by Eq. (31), attractive or repulsive p-wave interaction may contribute to the superconductivity of anomalous type. Independently of the type of the interactions, such an anomalous phase disappears, when one of the SFS disappears due to the stronger spin-orbit coupling.

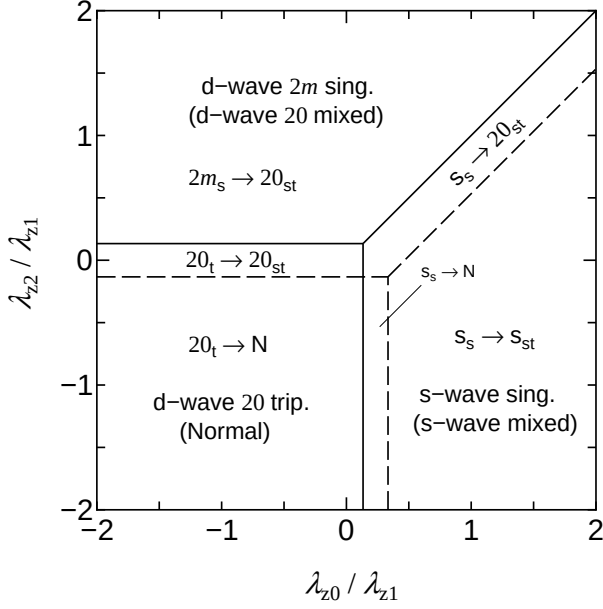


FIG. 6: Phase diagrams and the transitions for the Ising-type interaction with attractive p-wave components. Solid and broken lines are the phase boundaries in case (i) and case (ii), respectively. The states for the latter case are shown in the brackets. The notation “2m” means the d-wave state with quantum number $(2, m)$ (see the text). The other legends are shown in the caption of Fig. 4.

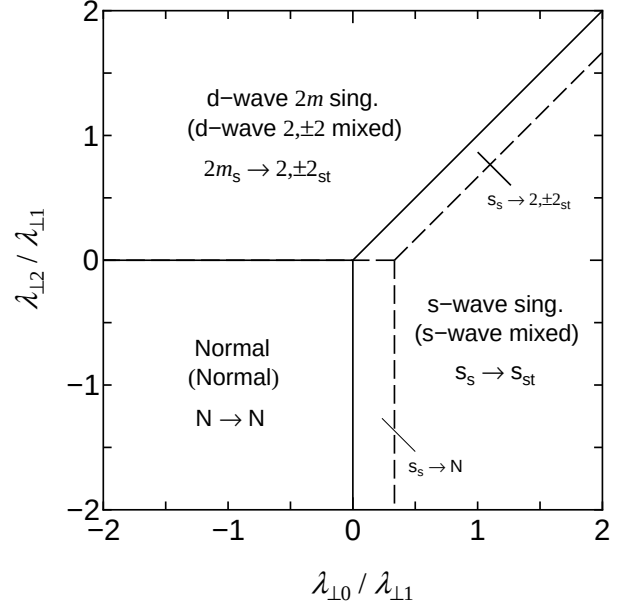


FIG. 8: Phase diagrams and the transitions for the planar spin interaction with attractive p-wave components. The legends are shown in the captions of Figs. 4 and 6.

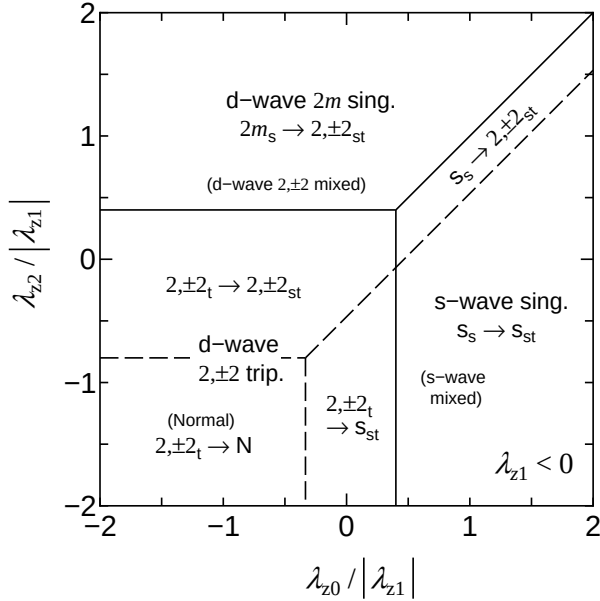


FIG. 7: Phase diagrams and the transitions for the Ising-type interaction with repulsive p-wave components. The legends are shown in the captions of Figs. 4 and 6.

Type of interaction	coupling constants	p-wave component	
		$\lambda_1 > 0$	$\lambda_1 < 0$
Ising	$J_z \neq 0, J_\perp = 0$	Fig. 6	Fig. 7
Planar	$J_z = 0, J_\perp \neq 0$	Fig. 8	Fig. 9
Isotropic	$J_z = J_\perp \equiv J$	Fig. 10	Fig. 11

TABLE I: Table of the phase diagrams.

5. Transitions from the full-gap state to the line-node state

The FLT due to the disappearance of one of the SFS occurs also for the SI as shown in Figs. 6 - 11, which are summarized in Table II. Practically, we can regard the d-wave states as line-node states, even when they degenerate with respect to m , by the argument in Sec. VI A.

In these phase diagrams, the regions where the FLT occurs are narrower than that in the phase diagram (Fig. 4) for the CI. Furthermore, it seems difficult that the s-wave component becomes attractive for the interactions of magnetic origin. If we exclude such a situation, the remaining possibilities are planar spin interaction and isotropic spin interaction with $\lambda_1 < 0$. However, in those cases, the FLT occurs only in small regions, in which the pairing interaction is very weak. Therefore, in the present theory, if the FLT occurs, it is most likely that the CI is the most dominant pairing interaction.

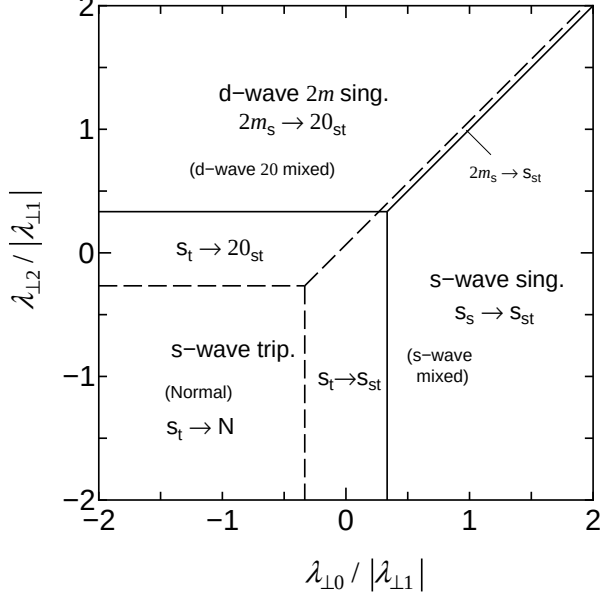


FIG. 9: Phase diagrams and the transitions for the planar spin interaction with repulsive p-wave components. The legends are shown in the captions of Figs. 4 and 6.

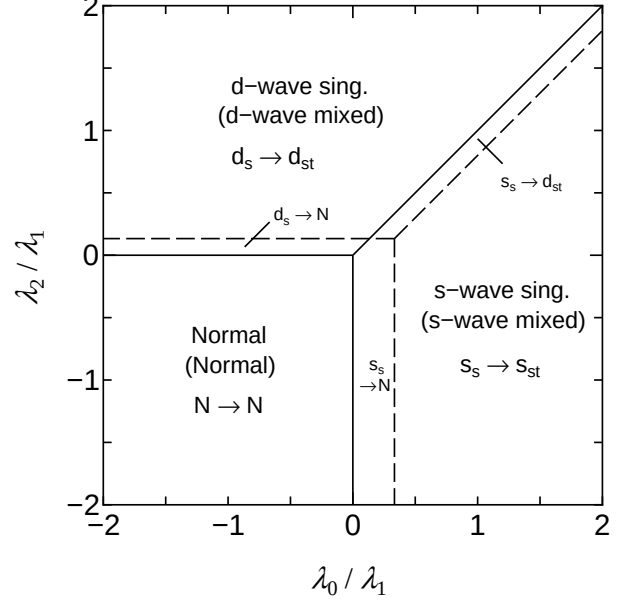


FIG. 10: Phase diagrams and the transitions for the isotropic spin interaction with attractive p-wave components. The legends are shown in the captions of Figs. 4 and 6.

Type of interaction	Sign of λ_l			FLT $s \rightarrow d(l, m)$	Phase diagram
	s	p	d		
Charge	-	+	+	$S_t \rightarrow d(2, m)$	Fig. 4
	+	-	+	$S_s \rightarrow d(2, m)$	Fig. 5
Ising spin	+	+	+	$S_s \rightarrow d(2, 0)$	Fig. 6
	+	-	+	$S_s \rightarrow d(2, \pm 2)$	Fig. 7
Planar spin	+	+	+	$S_s \rightarrow d(2, \pm 2)$	Fig. 8
	-	-	$\pm$	$S_t \rightarrow d(2, 0)$	Fig. 9
Isotropic spin	+	+	+	$S_s \rightarrow d(2, m)$	Fig. 10
	-	-	$\pm$	$S_t \rightarrow d(2, m)$	Fig. 11

TABLE II: Relation between the type of the interactions and the signs of the coupling constants for the FLT to occur. In each phase diagram, the signs are those for the major part of the area in which the FLT occurs. The double sign $\pm$ means that λ_2 can take either sign, but the absolute value is small. “ S_s ” and “ S_t ” denote the s-wave spin-singlet and triplet states, respectively.

VII. SUMMARY AND DISCUSSION

We have examined the superconductivity in noncentrosymmetric systems with various types of interactions between electrons. We have presented a formulation of the superconductivity, and obtained the transition temperatures and the gap functions, including the results that have been obtained by previous authors [1–3, 8]. We have derived the pairing interactions Eq. (30) between the two electrons on the SFS from the interactions between original electrons. Transformation matrices $\mathcal{T}_{X\alpha\alpha'}^{(ss')}$ for three types of interactions V_{ij}^c , J_{ij}^z , and $J_{ij}^\perp$ are ob-

tained. We have examined two kinds of order-parameter mixing effects in such superconductors due to the strong spin-orbit coupling: One is the parity mixing of the spin-singlet pairs $\langle \hat{d}_0(\mathbf{k}) \rangle$ and the triplet pairs $\langle \hat{d}(\mathbf{k}) \rangle$, and another is the inter-band mixing of the pairs on the different SFS, *i.e.*, $\langle \hat{\psi}_{++}(\mathbf{k}) \rangle$ and $\langle \hat{\psi}_{--}(\mathbf{k}) \rangle$, due to the inter-band pair hopping.

First, we have examined the equal-band limit, where λ_s , λ'_s , and $\omega_c^{(s)}$ do not depend on the band index $s = \pm$. We should note that this limit does not imply the absence of the spin-orbit coupling, because the split of the Fermi surfaces is taken into account by setting $\langle \hat{\psi}_{\pm\mp}(\mathbf{k}) \rangle = 0$. In this limit, since the parity mixing effect is suppressed, a pure spin-singlet state or a pure spin-triplet state occurs, while the inter-band mixing effect becomes the most efficient. Secondly, we have examined the single-band limit, where $\rho_-(0) = 0$. In this limit, the amplitudes of the spin-singlet and triplet components coincide, in contrast to the equal-band limit. When one of the SFS disappears, the inter-band mixing effect disappears, while the singlet-triplet mixing effect becomes the most efficient. Between these two limits, drastic changes explained below take place.

It is found that inter-band interactions could enhance the superconducting transition temperature T_c remarkably, even if they are very small, as demonstrated in Fig. 1. For example, when $\lambda_+ = 0.2$, $\lambda_- = 0.1$, and $\omega_c^{(-)}/\omega_c^{(+)} = 2$, the T_c 's of independent bands ($\lambda'_+ = \lambda'_- = 0$) are estimated as $T_{c0}^{(+)} / 1.13\omega_c^{(+)} \approx 0.00764$ and $T_{c0}^{(-)} \approx 0.0135 \times T_{c0}^{(+)} \ll T_{c0}^{(+)}$. In this case, small inter-

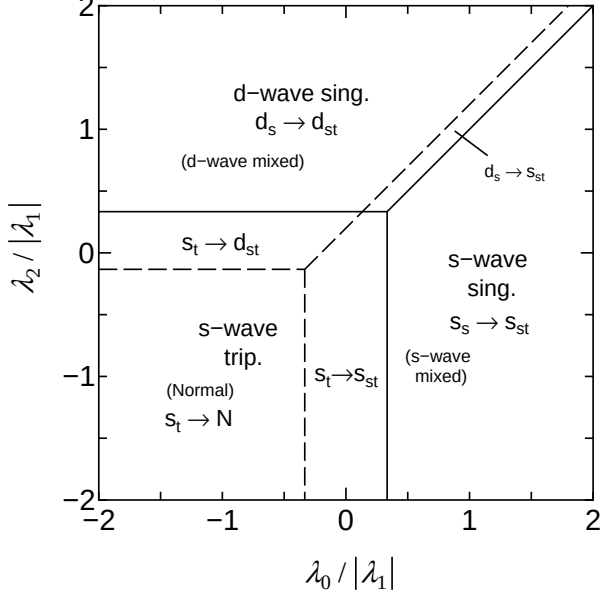


FIG. 11: Phase diagrams and the transitions for the isotropic spin interaction with repulsive p-wave components. The legends are shown in the captions of Figs. 4 and 6.

band interactions, such as $\lambda'_+ = \lambda'_- = 0.1$, enhance the transition temperature up to $T_c \approx 3.96 \times T_{c0}^{(+)} \gg T_{c0}^{(+)}$.

This effect may partly explain large difference of T_c 's observed in $\text{Li}_2\text{Pd}_3\text{B}$ and $\text{Li}_2\text{Pt}_3\text{B}$ (7 K and 2.7 K, respectively). In the latter compound, some of the Fermi surfaces lose their partners due to stronger spin-orbit coupling [10], and they are not benefited from the inter-band mixing effect. This explanation is the case, if the Fermi-surfaces without partners dominate the superconductivity in the latter compound. Their contributions to the density of states are large, according to the first principle calculation by Shishidou and Oguchi [10].

In addition, we have examined the effect of the difference of the two effective cutoff energies $\omega_c^{(+)}$ and $\omega_c^{(-)}$. The difference can be large in the interactions mediated by spin and charge fluctuations, because each pair of the Fermi-surfaces has a different nesting condition, which is sensitive to the shape of the Fermi-surfaces. It is found that the transition temperature strongly depends on the ratio $\omega_c^{(-)}/\omega_c^{(+)}$ as shown in Fig. 1.

Next, we have examined models with spherically symmetric Fermi-surfaces and $\hat{g}(\mathbf{k}) = \hat{\mathbf{k}}$ as an example. The resultant phase diagrams drastically change when one of the SFS disappears. In particular, we have derived the areas where the transition from the full-gap state to the line-node state (FLT) occurs. The FLT occurs in many cases, but analyzing the phase diagrams, it is found that it occurs in a wider and realistic parameter region for the CI, while it does in rather narrower and unrealistic parameter regions for the SI. Therefore, the CI would

be the dominant pairing interaction in many of the systems in which the FLT is observed. When the s-wave interaction is strongly repulsive, for example due to the strong on-site (screened) Coulomb repulsion, and the p-wave and d-wave interactions are attractive, we obtain a large region where the FLT occurs (see Fig. 4).

Therefore, the inexistence of the partners in some of the SFS in $\text{Li}_2\text{Pt}_3\text{B}$, which has been found by Shishidou and Oguchi [10], may play an essential role in the differences of the superconductivity in $\text{Li}_2\text{Pt}_3\text{B}$ from that in $\text{Li}_2\text{Pd}_3\text{B}$. If the FLT occurs and the present scenario is the case in these compounds, it is most likely that the full-gap state in $\text{Li}_2\text{Pd}_3\text{B}$ and the line-node state in $\text{Li}_2\text{Pt}_3\text{B}$ are an s-wave nearly-spin-triplet state and a d-wave state that has both spin-singlet and triplet components of comparable weights, which are induced by the CI. On the other hand, if the full-gap state occurs also in $\text{Li}_2\text{Pt}_3\text{B}$ [16], the both states are of s-wave pairing, but that is a nearly spin-singlet state in $\text{Li}_2\text{Pd}_3\text{B}$ and a singlet-triplet mixed state of comparable weights in $\text{Li}_2\text{Pt}_3\text{B}$.

Type of the interaction	Sign of λ_i			Anomalous triplet state
	s	p	d	
Charge	$\pm$	$+$	$\pm$	s-wave
Ising spin	$-$	$+$	$-$	d-wave, Y_{20}
	$-$	$-$	$-$	d-wave, $Y_{2,\pm 2}$
Planar spin	$-$	$-$	$-$	s-wave
Isotropic spin	$-$	$-$	$-$	s-wave

TABLE III: Anomalous spin-triplet states and the properties of the interactions. The signs are those for the major parts of the areas in which the anomalous spin-triplet states occur. Strictly, see corresponding phase diagrams. + sign means the interaction is attractive between original electrons.

It is found that the magnetically mediated pairing interaction can induce the d-wave spin-triplet states as well as the s-wave spin-triplet state. We summarize the relation between the anomalous spin-triplet states and the properties of the interaction in Table III. The magnetic anisotropy of the Ising-type interaction plays an essential role in the occurrence of the d-wave spin-triplet states as summarized in Table III. The terms $2\lambda_{z1}/15$ in λ_{20} and λ'_{20} and the terms $-4\lambda_{z1}/5$ in $\lambda_{2,\pm 2}$ and $\lambda'_{2,\pm 2}$ in Eq. (43) induce the d-wave spin-triplet states, when $\lambda_{z1} > 0$ and $\lambda_{z1} < 0$, respectively. Furthermore, when the spin-spin interaction is planar or isotropic, repulsive p-wave interaction can induce the s-wave spin-triplet state, if the even-parity interactions are repulsive or weak.

Lastly, we discuss the experimental result of the Knight-shift in $\text{Li}_2\text{Pt}_3\text{B}$ [14], which exhibits a flat temperature dependence. As we mentioned in Sec. I, it seems that conventional theory could not explain this result. If we assume that the spin susceptibility remains unchanged across T_c , we obtain that $\langle \hat{d}_z(\mathbf{k}) \rangle = \langle \hat{d}_0(\mathbf{k}) \rangle = 0$ for majority of $\mathbf{k}$'s. Since $\langle \hat{d}_z(\mathbf{k}) \rangle = \langle \hat{d}(\mathbf{k}) \rangle \hat{g}_z(\mathbf{k})$, we

obtain $\langle \hat{d}(\mathbf{k}) \rangle = 0$ or $\hat{g}_z(\mathbf{k}) = \cos \bar{\theta}_{\mathbf{k}} = 0$. Therefore, this leads to a contradiction that all the superconducting gap functions vanish as $\langle \hat{d}(\mathbf{k}) \rangle = \langle \hat{d}(\mathbf{k}) \rangle \hat{g}(\mathbf{k}) = \mathbf{0}$ and $\langle d_0(\mathbf{k}) \rangle = 0$, unless the superconductivity occurs mainly on parts of Fermi surfaces in which $\bar{\theta}_{\mathbf{k}} = \pi/2$ is satisfied. However, in $\text{Li}_2\text{Pt}_3\text{B}$, since the sample was powder, the angles between the magnetic field and the crystal axes would have distributed randomly. One of the possible explanations is that the states of the sample, such as the gap function of the superconductivity and orientations of the powders, are considerably affected by the magnetic field applied for the measurement. The theoretical interpretation of the behavior of the Knight-shift remains for the future.

In conclusion, the superconductivity in noncentrosymmetric system drastically changes when one of the SFS vanishes as the spin-orbit coupling increases. For example, the gap structures, the transition temperatures, and the phase diagrams are quite different depending on whether both the SFS exist or not. In particular, in some conditions, the FLT occurs when one of the SFS disappears. The area of the FLT in the phase diagram is the largest, when the pairing interaction is the CI and the

condition $\lambda_{c1} > \lambda_{c2} > 0 > \lambda_{c0}$ is satisfied. The latter condition seems realistic in the real materials if we suppose the CI. Therefore, within the present theory, it is most likely that the CI is the dominant pairing interaction, in systems in which an FLT occurs, although possibilities of magnetically induced pairing interactions are not excluded. Anomalous superconducting states, such as s-wave and d-wave spin-triplet states, are induced by the attractive or repulsive p-wave spin-triplet interaction in the presence of the inter-band spin-triplet-pair hopping interactions which are active only when both of the SFS exist. These behaviors are sensitive to the type of the pairing interaction.

ACKNOWLEDGMENTS

The author wishes to thank T. Shishidou for useful discussions and informations on their results of the first principle calculations in $\text{Li}_2\text{Pd}_3\text{B}$ and $\text{Li}_2\text{Pt}_3\text{B}$. The author is very grateful to H. Tou for useful discussions and informations on practice and analysis in NMR experiments.

-
- [1] L.P. Gor'kov and E.I. Rashba, Phys. Rev. Lett. **87**, 037004 (2001).
 - [2] I.A. Sergienko and S.H. Curnoe, Phys. Rev. B **70**, 214510 (2004).
 - [3] P.A. Frigeri, D.F. Agterberg, A. Koga, and M. Sigrist, Phys. Rev. Lett. **92**, 097001 (2004).
 - [4] N. Hayashi, K. Wakabayashi, P.A. Frigeri, and M. Sigrist, Phys. Rev. B **73**, 024504 (2006); 092508 (2006).
 - [5] S. Fujimoto, Phys. Rev. B **72**, 024515 (2005).
 - [6] For a review, see S. Fujimoto, J. Phys. Soc. Jpn. **76** 051008 (2007), and references therein.
 - [7] Y. Yanase and M. Sigrist, J. Phys. Soc. Jpn. **76**, 043712 (2007).
 - [8] K.V. Samokhin and V.P. Mineev, Phys. Rev. B **77**, 104520 (2008).
 - [9] C.-K. Lu and S. Yip, Phys. Rev. B **77**, 054515 (2008).
 - [10] T. Shishidou and T. Oguchi, unpublished.
 - [11] K. Togano, P. Badica, Y. Nakamori, S. Orimo, H. Takeya, and K. Hirata, Phys. Rev. Lett. **93**, 247004 (2004).
 - [12] P. Badica, T. Kondo, and K. Togano, J. Phys. Soc. Jpn. **74**, 1014 (2005).
 - [13] M. Nishiyama, Y. Inada, and G.-q. Zheng, Phys. Rev. B **71**, 220505(R) (2005).
 - [14] M. Nishiyama, Y. Inada, and G.-q. Zheng, Phys. Rev. Lett. **98**, 047002 (2007).
 - [15] H.Q. Yuan, D.F. Agterberg, N. Hayashi, P. Badica, D. Vandervelde, K. Togano, M. Sigrist, and M.B. Salamon, Phys. Rev. Lett. **97**, 017006 (2006).
 - [16] P.S. Häfliger, R. Khasanov, R. Lortz, A. Petrović, K. Togano, C. Baines, B. Graneli, H. Keller, J. Supercond. Nov. Magn **22**, 337 (2009).
 - [17] D.C. Peets, G. Eguchi, M. Kriener, S. Harada, Sk.Md. Shamsuzzamen, Y. Inada, G.-Q. Zheng, and Y. Maeno, Phys. Rev. B **84**, 054521 (2011).
 - [18] H. Shimahara, J. Phys. Soc. Jpn. **72**, 1851 (2003).
 - [19] D. Fay and J. Appel, Phys. Rev. B **16**, 2325 (1977).
 - [20] For example, see Fig. 11(a) in H. Shimahara, J. Phys. Soc. Jpn. **58**, 1735 (1989).
 - [21] I.F. Foulkes and B.L. Gyorffy, Phys. Rev. B. **15**, 1395, (1977).